

Evidence for local lattice distortions in giant magnetocapacitive CdCr_2S_4

V. Gnezdilov¹, P. Lemmens², Yu. G. Pashkevich³, P. Scheib²,
 Ch. Payen⁴, K. Y. Choi⁵, J. Hemberger⁶, A. Loidl⁶, V. Tsurkan^{6,7}
¹ *B. I. Verkin Inst. for Low Temperature Physics, NASU, 61164 Kharkov, Ukraine;* ² *Inst. for Condensed Matter Physics, TU Braunschweig, D-38106 Braunschweig, Germany;* ³ *A. A. Galkin Donetsk Phystech NASU, 83114 Donetsk, Ukraine;* ⁴ *Inst. des Mat. Jean Rouxel, CNRS-IMN, B.P.32229, F-44322 Nantes, France;* ⁵ *NHMFL/FSU, Tallahassee, FL 32310-3706, USA;* ⁶ *Experimental Physics V, Center for Electronic Correlations and Magnetism, University of Augsburg, D-86135 Augsburg, Germany;* ⁷ *Inst. of Applied Physics, Academy of Sciences of Moldova, MD-2028 Chisinau, R. Moldova*
 (Dated: February 6, 2008)

Raman scattering experiments on CdCr_2S_4 single crystals show pronounced anomalies in intensity and frequency of optical phonon modes with an onset temperature $T^*=130$ K that coincides with the regime of giant magnetocapacitive effects. A loss of inversion symmetry and Cr off-centering are deduced from the observation of longitudinal optical and formerly infrared active modes for $T < T_c = 84$ K. The intensity anomalies are attributed to the enhanced electronic polarizability of displacements that modulate the Cr-S distance and respective hybridization. Photo doping leads to an annihilation of the symmetry reduction. Our scenario of multiferroic effects is based on the near degeneracy of polar and nonpolar modes and the additional low energy scale due to hybridization.

PACS numbers: 72.80.Ga, 75.30.-m, 71.30.+h, 78.30.-j

Recently the coexistence and mutual coupling of magnetic and dielectric properties are discussed from both fundamental and application point of view¹. Large coupling effects have been found in different material classes, ranging from antiferromagnets (AF) with spiral ground states, via lone pair systems with hybridized electronic states that gain energy by polar distortions² to composite or lamellar materials that provide magneto-elastic coupling via interfaces³. The intrinsic coexistence of these order parameters is hindered by the exclusive conditions of having occupied 3d electron states to provide magnetic exchange and their energetic disadvantage in polar distorted coordinations⁴.

Among the reported materials, the cubic thio-spinel CdCr_2S_4 stands out due to its large ferromagnetic (FM) moment ($T_c = 84$ K) coexistent with a remanent dielectric polarization. Furthermore, a pronounced fluctuation regime with relaxor ferroelectric behavior⁵ and evidence for polar nanodomains exists. This is evident from a maximum of the dielectric loss at $T_{max}(\omega \rightarrow 0) = T^* = 130$ K and a broadening of X-ray peaks⁶. Therefore, relaxation effects, local polar distortions and variations of the electronic state may play an important role for the magnetocapacitive effects⁷. Similar to manganites the cross susceptibilities could be magnified by microscopic phase separation⁹. Also with respect to the magnetic phase diagram CdCr_2S_4 is at some borderline. The related HgCr_2S_4 with a very similar Cr-Cr separation and Curie-Weiss constant is a non-collinear AF⁸. On the other hand there is evidence for a nonintrinsic nature of some phenomena. Problems^{7,10} arise due to the centrosymmetric room temperature crystal structure, the finite conductivity that impedes the dielectric characterization and the inevitable sulphur non-stoichiometry of otherwise excel-

lent crystals. Nevertheless, record values of magnetocapacitive effects with an increase of the dielectric constant ϵ' of up to a factor of 30 in a magnetic field of 10 T are reported⁷. Due to the lack of microscopic information the understanding of the underlying physics is rather limited and requires further spectroscopic investigations.

In the present Letter, the observation of pronounced anomalies of the phonon systems based on Raman light scattering (RS) on single crystals is reported. We conclude a non-centrosymmetric $F\bar{4}3m$ crystal structure at low temperatures which clears up a long standing dispute on a possible Cr off-centering and frozen A_{2u} displacement. Modes that modulate the Cr-S distances show large intensity gains and point to an intrinsic coupling effect of the exchange splitting and hybridization to local polarizabilities.

Earlier RS experiments^{11,12,13} showed agreement with factor group calculations for the room temperature structure $Fd\bar{3}m$, that is cubic and inversion symmetric¹⁴. The decomposition of the Raman-active symmetry components leads to $\Gamma = A_{1g}(394) + E_{1g}(257) + 3 \cdot T_{2g}(99, 280, 352)$ with the calculated phonon frequencies given in brackets (cm^{-1})^{10,14}. Our RS experiments were performed on as-grown, shiny [111] surfaces of CdCr_2S_4 single crystals grown by Cl transport. On the same sample batch the giant magnetocapacitive effects have been reported⁵. We used the excitation wavelength $\lambda = 632.8$ nm of a HeNe laser with a power level $P = 6$ mW, i.e. a factor 15 smaller than in a previous study^{11,13}. In all experiments we used crossed (xy) light polarization that allows the observation of all phonon modes.

In Fig. 1 Raman spectra of CdCr_2S_4 are presented. At room temperature very sharp maxima are observed thus proving the high quality of the single crystals. The

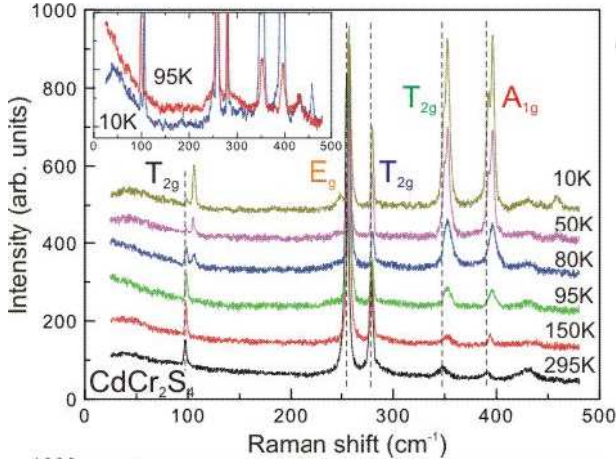


FIG. 1: RS spectra of CdCr_2S_4 as function of temperature. The curves are shifted for clarity. The phonon lines are marked by dashed lines and assigned according to the high temperature structure¹⁴. The inset shows a depression of the the background intensity for $T=10$ K.

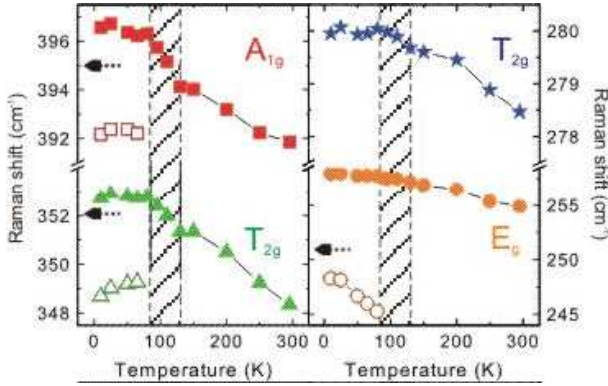


FIG. 2: RS phonon frequency of CdCr_2S_4 as function of temperature for the high frequency and the low frequency modes on the left and right panels, respectively. The fluctuation regime between $T_c=84$ K and $T^*=130$ K is marked by a dashed bar. Arrows mark the frequency of LO phonons at $T=10$ K from earlier IR absorption experiments¹⁵.

number and frequencies of the excitations are in detailed agreement with lattice calculations¹⁰ based on the space group $Fd3m$. They are marked by dashed lines and with the respective symmetry representation. With decreasing temperature several anomalies develop. Most spectacular is the appearance of a new mode at 104 cm^{-1} , i.e. 6 cm^{-1} higher than the lowest frequency mode at 98 cm^{-1} . At the same time, the two high frequency phonons with $\Delta\omega > 300 \text{ cm}^{-1}$ show an enormous gain of intensity. These modes are already broadened at room temperature compared to the modes with $\Delta\omega < 300 \text{ cm}^{-1}$. In the inset of Fig. 1 we show evidence for a depression of the background scattering with the onset of magnetic order in the same energy range.

While in proximity of the 352-cm^{-1} T_{2g} mode and the 396-cm^{-1} A_{1g} mode the evolution of sidebands is observed

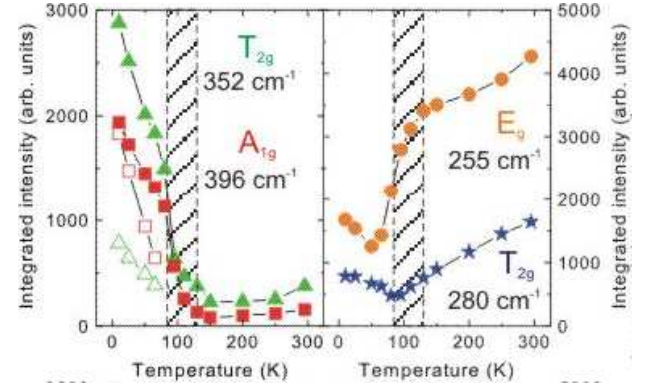


FIG. 3: Integrated RS intensity of CdCr_2S_4 as function of temperature for the high energy and the low energy modes in the right panel. The open symbols correspond to the low temperature modes at 349 and 392 cm^{-1} , respectively.

at low temperatures, the T_{2g} mode at 280 cm^{-1} does not split, see Fig. 2. The temperature dependence of the peak frequencies shows a kink at T^* and sidebands appear for $T < T_c$. The splittings themselves are rather small and of the order of 1-2% for the high frequency modes. These observations are not compatible with a large reduction of symmetry and point to a preserved cubic symmetry. In the same figure the frequencies of the low-temperature longitudinal optical (LO) modes from an earlier infrared absorption experiment are given by arrows¹⁵. It is obvious that the observed new modes are very close or coincide with these data. For the 280-cm^{-1} T_{2g} mode no corresponding LO phonon exists¹⁶ and therefore no splitting can be detected. We attribute the additional modes in RS to a loss of inversion symmetry. In cubic systems and back scattering geometry only LO phonons, formerly IR active modes, develop a scattering cross section in RS.

In Fig. 3 the phonon intensities of the high temperature Raman active modes and additional modes are given. Both characteristic temperatures are evident in the data. Noteworthy is the large enhancement of the high frequency T_{2g} and A_{1g} modes in the fluctuation regime between T_c and T^* . It leads to an overall increase by a factor 25 and 12.5 to low temperatures, respectively. Interestingly, the intensity of the LO phonons increases with a similar slope down to lowest temperatures. In contrast the intensity of the 280-cm^{-1} and the 255-cm^{-1} modes both drop by 70% in the high temperature regime and recover only to about 1/3 of this intensity at low temperatures. The RS intensity of a phonon mode consists of the scattering volume multiplied by the electronic polarizability with respect to the particular mode. As the scattering volume and optical penetration depth develop in parallel for all modes the observed anomalies must at least be partly related to the local enhancement of electronic polarizability.

The left panel of Fig. 4 shows low energy T_{2g} and the related LO mode close to T_c . These modes show

the largest splitting which facilitates their discrimination. With the onset of FM order the T_{2g} mode is damped, broadened and recovers only at lowest temperatures with a remaining asymmetric line shape. The LO appears clearly at the magnetic transition. This behavior is different from the intensity gain that the high energy T_{2g} mode shows for temperatures around T^* . At lowest temperature the intensity of the sideband is comparable to the high temperature intensity of the T_{2g} mode.

Using the internal photo effect over the gap $\Delta=1.6-1.8$ eV¹⁷ the local electronic properties of CdCr_2S_4 can be modified¹⁸. Resonant RS with circular polarized light and effects of optical pumping have been demonstrated earlier¹² and attributed to an electron transfer from the highly structured valence band of hybridized Cr t_{2g} - S 2p states to the unoccupied Cr e_g - Cd s high energy continuum¹⁰. Our RS data suggest a strong coupling of the phonon system to exactly these states. In Figs. 4b and c we compare RS with the previously used excitation wavelength $\lambda=632.8$ nm (1.97 eV) and 488 nm (2.55 eV), respectively. The difference is rather drastic. A reversal of the effect of temperature on the RS spectra is evident, i.e. the intensity ratio of the T_{2g} to the LO phonon with 488 nm is close to that at $T \approx T_c$ with 632.8 nm. This intrinsic effect cannot be attributed to a change of the selection rules or penetration depth as the intensities of both modes are affected. It must be related to a local occupation of the antibonding Cr e_g - Cd s states within the conduction band.

Understanding the anomalous behavior of CdCr_2S_4 involves two important issues. The first addresses the inconsistency between the high temperature structure and the observed properties, i.e. global or local deviations from inversion symmetry. The second question concerns the interplay between polar distortions and the spin polarization, i.e. the magnetocapacitive coupling mechanism. It has to be outlined that true multiferrocity depends on a nonlinear relation between the corresponding fields and susceptibilities via the cross relations between magnetic, dielectric and lattice degrees of freedom^{2,4}.

It is clear from our RS data that in CdCr_2S_4 the inversion symmetry is lost and the resulting low temperature symmetry is moderately reduced from $\text{Fd}\bar{3}\text{m}$ to $\text{F}\bar{4}3\text{m}$ ¹⁹. The observed sidebands are a result of the related A_{2u} displacement that evolves into a long range distortion for $T < T_c$. The depression of the continuum of scattering with energies $\Delta\omega < 300$ cm^{-1} in Fig. 1 is further evidence for the suppression of fluctuations. As shown in Fig. 5 a frozen A_{2u} mode corresponds to the long suggested Cr-off centering¹⁰. The preserved cubic symmetry is the only way to describe the observed excitation spectrum¹⁹.

The intensity/polarizability enhancements of all high frequency modes are strong evidence for pronounced nonlinearities of the coupled electronic-lattice systems. The intensity of these modes and the LO sidebands is still increasing in a temperature range where the macroscopic magnetization does not change so much⁵. In Fig. 5 we sketch displacements with enhanced polarizability and it

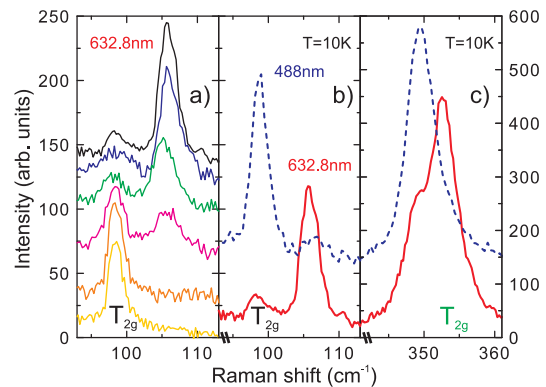


FIG. 4: a) Evolution of the low frequency T_{2g} mode with temperature with an exciting Laser wavelength of $\lambda=632.8$ nm at $T=10, 25, 65, 80, 95, 110$ K, from top to bottom. b) and c) RS experiments with $\lambda=488$ nm (top, dashed line) and 632.8 nm (bottom) at $T=10$ K. Curves have been shifted for clarity.

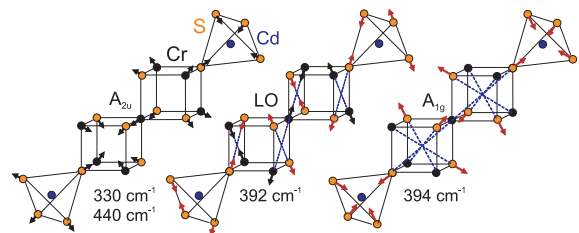


FIG. 5: Displacement patterns of modes that lead to a large modulation of the Cr-S hybridization^{14,23}.

is evident that all modes effectively modulate the hybridization of the Cr t_{2g} - S 2p states by a simultaneous stretching - squeezing of the S-Cd and S-Cr bonds, respectively^{11,14}. In contrast the intermediate frequency modes show an antiphase stretching on the opposite sides of the S-Cr cube. Depending on the relative amplitude of the Cr and S displacements such a motion can cancel the contribution of all S-Cr bonds to the dielectric response as well as to the RS response. Noteworthy, the intensity of the corresponding 255- cm^{-1} mode shows a minimum below T_c . The given displacements could also be interpreted as a Cr-Cr dimer formation. Such structural correlations lead to large energy gains on low dimensional or frustrated topologies, i.e. it is responsible for the spin gap formation in MgTi_2O_4 ²⁰ and CuIr_2S_4 ²¹. For CdCr_2S_4 the hybridized states including some sulphur nonstoichiometry provide a finite but small density of states at the Fermi energy²². Anticipating a feedback of the exchange splitting with local distortions we expect insulating FM domains that spatially fluctuate and are only weakly coupled by the slower polar strain fields on larger length scales. Such a scenario of different length and energy scales involved in the fluctuation regime of CdCr_2S_4 is also supported by the observed structural and dielectric anomalies^{5,6}.

The presently discussed multiferroics provide a rather

complex picture of possible mechanisms for large cross susceptibilities¹. As CdCr_2S_4 is a soft FM, spin frustration and canted moments can evidently be discarded. A different approach is based on the hybridization of nearly degenerate electronic states of appropriate symmetry, called second order Jahn-Teller effect^{2,4}. This effect induces a further low energy scale in the system and is responsible for off-centering, static or dynamic disorder and first order phase transitions^{24,25}. In certain cases it can overcompensate the cost of Coulomb energy due to the distortions of occupied 3d electron systems. In the multiferroic BiFeO_3 the off-centering of Bi is a result of a hybridization of both the Bi $6s^2$ and unoccupied $6p^0$ states with O 2p orbitals leading to a highly polarizable lone pair on one side of the Bi ion^{26,27}. Weaker displacements or dynamic effects are expected for Cd^{2+} ions²⁸. Indeed for CdCr_2S_4 there is no evidence for a static lone pair formation of Cd and S states. Nevertheless, the enhanced local polarizabilities of diagonal S displacements and photo-doping point to an electronic mechanism related to hybridization effects. Noteworthy is that the Cr t_{2g} - S 2p states strongly couple to the essential distortions of the spinel structure and that these states are at

least moderately correlated¹⁰. The spinel structure provides another peculiarity supporting our scenario. The energy splitting between polar and nonpolar modes in CdCr_2S_4 is extremely small compared to other energy scales of the system. This can be understood as a negligible restoring force or anisotropy towards higher order polar distortions. More direct evidence, however, has to come from high resolution diffraction on possible smeared-out electronic distribution within the S_6 octahedra or a large atomic displacement parameter of Cd^{2+} above T_c .

The observation of an inversion loss and an enhanced polarizability of Cr-S displacements with dimer-like correlations have lead us to develop a scenario based on hybridization effects to explain the colossal magnetocapacitive effects in CdCr_2S_4 . Thereby we have shown evidence for the intrinsic nature of the cross susceptibilities and related the extended fluctuation regime with polar nano domains to an additional, hybridization-induced low energy scale. Future investigations will show whether this model can also be used to understand related instabilities in other spinels and to find more systems with an application relevant parameter space.

-
- ¹ T. Kimura, et al., Nature (London) **426**, 55 (2003); N. Hur, et al., ibid. **429**, 392 (2004); Th. Lottermoser, et al., ibid. **430**, 541 (2004); T. Goto, et al., Phys. Rev. Lett. **92**, 257201 (2004); N. Hur, et al., ibid. **93**, 107207 (2004); B. B. Van Aken, et al., Nature Materials **3**, 164 (2004).
- ² M. Fiebig, J. Phys. D: Appl. Phys. **38**, R123 (2005).
- ³ H. Zheng, et al., Science **303**, 661 (2004); I. Levin, et al., Adv. Matter **18**, 2044 (2006).
- ⁴ N. A. Spaldin and M. Fiebig, Science **309**, 391 (2005); C. Ederer and N. A. Spaldin, Current Opinion in Solid State and Materials Science **9**, 128-139 (2005); N.A. Hill, J. Phys. Chem. B **104**, 6694-6709 (2000).
- ⁵ J. Hemberger, et al., Nature (London) **434**, 364 (2005).
- ⁶ H. Göbel, Journ. Mag. Magn. Mater. **3**, 143 (1976).
- ⁷ P. Lunkenheimer, et al., Phys. Rev. B **72**, 060103(R) (2005).
- ⁸ T. Rudolf, et al., cond-mat/0701080 (2007) and references therein.
- ⁹ E. Dagotto, *Phase Separation and Colossal Magnetoresistance*, (Springer, Berlin) 2002.
- ¹⁰ C. J. Fennie and K. M. Rabe, Phys. Rev. B **72**, 214123 (2005).
- ¹¹ E. F. Steigmeier and G. Harbecke, Phys. kondens. Materie **12**, 1, (1970).
- ¹² N. Koshizuka, et al., Phys. Rev. B **21**, 1316 (1980) and references therein; N. Sanford, et al., Phys. Rev. Lett. **50**, 1803 (1983).
- ¹³ Intensity anomalies of all phonon modes in Ref. 11 are spurious due to a strongly temperature dependent reference mode. A later study did not have sufficient resolution to observe small frequency splittings¹².
- ¹⁴ J. Zwinscher, et al., Journ. Solid State Chem. **118**, 43 (1995) and references therein.
- ¹⁵ K. Wakamura, T. Arai, J. Appl. Phys. **63**, 5824 (1988).
- ¹⁶ IR modes at T=10K have been reported in Ref. 15 as LO modes at 105.2, 251.2, 352.1, 395.0 and as TO modes at 101.8, 248.8, 323.5 and 379.0 cm^{-1} .
- ¹⁷ W. J. Miniscalco, et al., Phys. Rev. B **25**, 2947 (1982).
- ¹⁸ G. Güntherodt and R. Zeyher, in *Light Scattering in Solids IV*, edited by G. Güntherodt and M. Cardona (Springer, Berlin, 1984) and references therein.
- ¹⁹ Cubic symmetry is conserved by A_{2u} with Cr and S displacements, two nonequivalent Cr sites and two alternating S-Cd bond lengths, i.e. Cr dimers. The sites are 4a-Cd(1), 4d-Cd(2), 16e-Cr, 16e-S(1), 16e-S(2) with RS modes $\Gamma=3A_1+3E+7T_2$ enlarged by the former $2A_{2u}$ and $2E_u$ silent modes related to S- and Cr-displacements as well by $4T_{1u}$ of far infrared modes. Calculations give A_{2u} modes²³ at 331 and 422 cm^{-1} . The broader structure in Fig. 1 around 440-460 cm^{-1} for $T < T_c$ may also be multi-phonon scattering.
- ²⁰ M. Isobe, et al., Journ. Phys. Soc. Jap. **71**, 1848 (2002).
- ²¹ P. G. Radaelli, et al., Nature **416**, 155 (2002).
- ²² N. Shanthi, et al., J. Solid State Chem. **155**, 198 (2000).
- ²³ H. D. Lutz, et al., Z. Naturforsch. A **45**, 893 (1990).
- ²⁴ R. G. Pearson, Proc. Nat. Acad. Sci. USA **72**, 2104 (1975).
- ²⁵ J. K. Burdett and O. Eisenstein, Inorg. Chem. **31**, 1758 (1992).
- ²⁶ R. Seshadri, et al., Chem. Mater. **13**, 2892 (2001).
- ²⁷ J. B. Neaton, et al., Phys. Rev. B **71**, 014113 (2005).
- ²⁸ CdPS_3 is a respective example for Cd^{2+} off-centering in sulphur environments that leads to a structural transitions, see, e.g. F. Boucher, et al., Acta Cryst. B **51**, 952 (1995).